

Spin waves in terbium. III. Magnetic anisotropy at zero wave vector

J. G. Houmann and J. Jensen

Danish Atomic Energy Commission Research Establishment Risø, Roskilde, Denmark

P. Touborg

Technical University, Lyngby, Denmark

(Received 6 May 1974)

The energy gap at zero wave vector in the spin-wave dispersion relation of ferromagnetic Tb has been studied by inelastic neutron scattering. The energy was measured as a function of temperature and applied magnetic field, and the dynamic anisotropy parameters were deduced from the results. The axial anisotropy is found to depend sensitively on the orientation of the magnetic moments in the basal plane. This behavior is shown to be a convincing indication of considerable two-ion contributions to the magnetic anisotropy at zero wave vector. With the exception of the sixfold basal-plane anisotropy of the unstrained lattice, the dynamic anisotropy parameters deduced from our results agree with macroscopic measurements both with respect to the magnitudes (at zero temperature) and the temperature dependences. The deviations observed cannot be explained by existing theories which include the effects of zero-point deviations from the fully aligned ground state, and we tentatively propose polarization-dependent two-ion couplings as their origin.

I. INTRODUCTION

In this paper we shall study the behavior of the energy gap which is present at zero wave vector in the spin-wave spectrum of Tb as a consequence of magnetic anisotropy. We shall utilize some of the results obtained in the two preceding papers concerning the spin waves in Tb, to be referred to as I and II (I: two-ion magnetic anisotropy; II: magnon-phonon interaction).

Because of the importance for the magnon energies of single-ion anisotropy in the long-wavelength limit, the general single-ion Hamiltonian for an hcp lattice is examined in detail. An explicit account of the magnetoelastic effects for a basal-plane ferromagnet is given, in which two-ion magnetoelastic couplings are also included. We touch on the discussion of a "frozen"- versus a "flexible"-lattice model, and it is argued that the frozen-lattice model is correct when zero-point deviations due to magnon-magnon and magnon-phonon interactions are neglected. Including anisotropic two-ion couplings in the spin Hamiltonian, we deduced a general expression for the energy gap of a basal-plane ferromagnet in I. Here we derive an expression for the energy gap in terms of static parameters which are determined by macroscopic experiments.

We have studied the spin-wave energy gap in Tb by inelastic neutron scattering. The energy gap as a function of magnetic field applied in the easy and hard directions in the basal plane was measured in a temperature range from 4.2 to 130 K. The results were corrected for the field dependence of the relative magnetization at finite tem-

peratures. The dynamic anisotropy parameters deduced by a least-squares fitting to the experimental results are comparable with the corresponding static parameters obtained from other measurements. Only the static and the dynamic values for the hexagonal anisotropy of the unstrained lattice fail to agree, which may be due to zero-point deviations. However, we suggest an alternative explanation. Finally, we discuss the possibility of large contributions to the magnetic anisotropy in the long-wavelength limit from anisotropic two-ion couplings and conclude that such contributions are very likely to occur.

II. SINGLE-ION AND TWO-ION ANISOTROPY

Starting from a general spin Hamiltonian of I an expression for the energy gap at zero wave vector in the spin-wave spectrum was deduced, Eqs. (21)–(25) of I, valid for a basal-plane ferromagnet. The different terms describing the properties of the energy gap in Tb, which we obtained by studying the field dependence of the energy, may be classified according to the expressions derived in I. Because of the importance of the single-ion terms in the long-wavelength limit of the magnons, we shall here examine explicitly the single-ion Hamiltonian, bearing in mind that two-ion anisotropic couplings may influence the energy gap, as is apparent from Eqs. (22) and (23) of I.

The electrostatic field in which the ions are situated affects the energy levels of the system. Because the crystal-field energies are small compared to the spin-orbit coupling of the $4f$ elec-

trons of the rare-earth ions, the electrostatic energy of these electrons may be written

$$\mathcal{H}_{\text{cf}} = \frac{1}{2} \sum_i \sum_{lm} \frac{1}{S_l} [V_{lm} \bar{O}_{l,m}(J_i) + (-1)^m V_{lm}^* \bar{O}_{l,-m}(J_i)], \quad m \geq 0, \quad (1)$$

using the Wigner-Eckart theorem. V_{lm} are the crystal-field parameters [corresponding to $K_{010}^{l,m}(0)$ in Eq. (7) of I]. The various other quantities occurring in (1) have been defined in I. Time-reversal symmetry requires l to be even, and in the case of f electrons only terms for which l is smaller than or equal to 6 will be present. The symmetry of the electric field, which corresponds to the symmetry of the lattice, allows a reduction of (1). The structure of the heavy-rare-earth metals implies that V_{lm} is real and m is equal to 0 or 6 in these metals, which reduces the number of independent crystal-field parameters to four.

If the angular moments in the crystal are magnetically ordered, the total magnetoelastic energy of the system may be reduced by deformations of the lattice. Mason¹ has derived a macroscopic expression for the magnetostriction, while Callen and Callen² have developed a phenomenological theory based on group-theoretical representations for the allowed strains. Following the notation of Callen and Callen and of Cooper,³ we may write the homogeneous strains which transform according to the irreducible representations Γ_α , Γ_γ , and Γ_ϵ of the point group of the hcp lattice:

$$\epsilon^{\alpha,1} = \epsilon_{11} + \epsilon_{22} + \epsilon_{33}, \quad \epsilon^{\alpha,2} = \epsilon_{33} - \frac{1}{3} \epsilon^{\alpha,1}, \quad (2a)$$

$$\epsilon^\gamma = \frac{1}{2}(\epsilon_{11} - \epsilon_{22}) + i\epsilon_{12}, \quad (2b)$$

$$\epsilon^\epsilon = \epsilon_{13} + i\epsilon_{23}, \quad (2c)$$

where the strains ϵ_{ij} are defined as usual in terms of the elastic displacements $\vec{u}(\vec{x}, t)$,

$$\epsilon_{ij} = \frac{1}{2} \left(\frac{\partial u_i}{\partial x_j} + \frac{\partial u_j}{\partial x_i} \right), \quad (3)$$

where the Cartesian 1, 2, and 3 axes are along an a , b , and c direction of the hcp lattice, respectively. The α strains are then symmetry-preserving dilatations along the c axis and in the basal plane, the γ strains are distortions of hexagonal symmetry of the basal plane, and the ϵ strains are c -axis shear modes. The elastic density associated with the homogeneous strains is

$$\mathcal{H}_e = \frac{1}{2} c_1^\alpha (\epsilon^{\alpha,1})^2 + c_{12}^\alpha \epsilon^{\alpha,1} \epsilon^{\alpha,2} + \frac{1}{2} c_2^\alpha (\epsilon^{\alpha,2})^2 + \frac{1}{2} c^\gamma \epsilon^\gamma (\epsilon^\gamma)^* + \frac{1}{2} c^\epsilon \epsilon^\epsilon (\epsilon^\epsilon)^*, \quad (4)$$

where the five independent elastic constants can

be expressed in terms of the Cartesian elastic constants c_{ij} , as in Cooper³ and Goodings and Southern.⁴ For the present purposes we shall define the reduced elastic constants

$$c_\gamma = (1/NJ) c^\gamma = (1/NJ) 2(c_{11} - c_{22}), \\ c_\epsilon = (1/NJ) c^\epsilon = (1/NJ) 4c_{44}, \quad (5)$$

where N is the number of ions per unit volume.

In the limit of small deformations, we can truncate a power expansion of the change of the crystal field at the first term linear in the strains. In this approximation, the modification of the crystal-field energy introduced by distortions of the lattice is exhaustively described by means of 17 independent single-ion parameters:

$$\mathcal{H}_{\text{cf-e}} = -\frac{1}{2} \sum_i \sum_l \frac{1}{S_l} \left(\sum_{m=0,6} (B_{lm}^{(1)} \epsilon^{\alpha,1} + B_{lm}^{(2)} \epsilon^{\alpha,2}) [\bar{O}_{l,m}(J_i) + \bar{O}_{l,-m}(J_i)] + \sum_{m=-1,5} B_{lm} [\epsilon^\epsilon \bar{O}_{l,m}(J_i) - (\epsilon^\epsilon)^* \bar{O}_{l,-m}(J_i)] + \sum_{m=-2,4} B_{lm} [\epsilon^\gamma \bar{O}_{l,m}(J_i) + (\epsilon^\gamma)^* \bar{O}_{l,-m}(J_i)] \right). \quad (6)$$

As in (1) we use a coordinate system with the z axis along the c direction, and l is again restricted to the value 2, 4, and 6. The effect on the energy gap of the magnetoelastic terms for which l is equal to 2 was first considered by Turov and Sharov⁵ and was later discussed at length by Cooper.³

The total magnetoelastic single-ion Hamiltonian is then a sum of the crystal field energy of the unstrained lattice, the elastic energy, and the energy of the coupling between the spin system and the lattice, $\mathcal{H}_{\text{cf-e}}$. In the presence of an external magnetic field, we must add the Zeeman energy \mathcal{H}_Z [Eq. (28) of I], and the single-ion Hamiltonian is then given by

$$\mathcal{H}_J = \mathcal{H}_{\text{cf}} + \mathcal{H}_e + \mathcal{H}_{\text{cf-e}} + \mathcal{H}_Z. \quad (7)$$

If anisotropic two-ion interactions between the magnetic moments are neglected, the presence of magnetic anisotropy is related to the single-ion anisotropy only. In most experiments and theoretical calculations on heavy-rare-earth metals, the two-ion coupling is assumed to be an isotropic Heisenberg interaction, [Eq. (1) of I]. We shall start with this assumption and consider later the possible effects of two-ion anisotropy.

In equilibrium the derivatives of the free energy with respect to the strains must be zero, e.g.,

$$\left\langle \frac{\partial \mathcal{H}_J}{(\partial \epsilon^\gamma)^*} \right\rangle = c^\gamma \bar{\epsilon}^\gamma - \sum_{l,m=-2,4} \frac{1}{S_l} B_{lm} \left\langle \sum_i \bar{O}_{l,-m}(J_i) \right\rangle = 0. \quad (8)$$

The γ and ϵ strains are zero unless the moments are ferromagnetically ordered, or, put in another way, the equilibrium strains are always homogeneous throughout the crystal. This is called the "lattice-clamping" effect and has been treated in detail by Evenson and Liu.⁵ The γ and ϵ contributions to the free energy are then zero in a conical or helically ordered phase. The lowering of the magnetoelastic energy in passing from the helical to ferromagnetic state is the basic driving force behind the ferromagnetic transition in⁷ Dy and probably also in Tb, as proposed by Cooper.^{3,8}

In the ferromagnetic phase of Tb, where the moments lie in the basal plane, the γ strains are related to the magnetostriction coefficients defined by Mason¹ in the following way:

$$\bar{\epsilon}^\gamma = C e^{2i\phi} - \frac{1}{2} A e^{-4i\phi}, \quad (9)$$

where ϕ is the angle between the direction of magnetization and the 1 axis. Combining (8) and (9), we obtain at zero temperature

$$C = \frac{1}{J c_\gamma} \sum_l B_{l2} \Gamma_{l,2}, \quad (10a)$$

$$A = -2 \frac{1}{J c_\gamma} \sum_l B_{l4} \Gamma_{l,4}, \quad (10b)$$

using the expectation values deduced in I for the Racah operators [(11)–(13)]. The magnetostriction coefficients, which have been determined experimentally for Tb by Rhyne and Legvold,⁹ are proportional to certain linear combinations of the coupling parameters defined in (6).

The ϵ -strain part of (6) vanishes for a basal-plane ferromagnet, which follows from the fact that $l+m$ is odd in this case. If $B_{66}^{(i)}$ in the α -strain part of (6) is neglected, this part may be taken into account by introducing the effective crystal-field parameters:

$$V'_{l0} = V_{l0} - (B_{l0}^{(1)} \bar{\epsilon}^{\alpha,1} + B_{l0}^{(2)} \bar{\epsilon}^{\alpha,2}). \quad (11)$$

Later we shall see that this approximation is acceptable in the case of Tb.

When the equilibrium strains are introduced in (7), the reduced magnetoelastic energy (in the case $\theta = \frac{1}{2}\pi$ and $T=0$ K) is

$$E_J = \frac{1}{NJ} \langle \mathcal{H}_J \rangle = \frac{1}{J} \sum_l \Gamma_{l,0} V'_{l0} - \frac{1}{2} c_\gamma C^2 - \frac{1}{8} c_\gamma A^2 + \left(\frac{1}{J} \Gamma_{6,6} V_{66} + \frac{1}{2} c_\gamma AC \right) \times \cos 6\phi - g\mu_B H \cos(\delta - \phi), \quad (12)$$

where δ is the angle between the direction of the applied field and the 1 axis. The sign of the coefficient of $\cos 6\phi$ determines the easy planar axis. This coefficient is positive in the case of Tb, which corresponds to an alignment of the moments parallel with a b axis ($\phi = \pi/6 + p\pi/3$) in the absence of an external field. If a field is applied along a hard planar axis ($\delta=0$) then the magnetization is pulled towards this direction, as described by the equation

$$g\mu_B H = g\mu_B H_c (\sin 6\phi) / 6 \sin \phi = g\mu_B H_c \frac{1}{3} (3 - 16 \sin^2 \phi + 16 \sin^4 \phi) \cos \phi, \quad (13)$$

as long as the field is smaller than the critical field H_c ,

$$g\mu_B H_c = 36(1/J) \Gamma_{6,6} V_{66} + 18c_\gamma AC. \quad (14)$$

At this field the moments are pulled fully around to the hard axis ($\phi=0$).

Because of the presence of magnetic anisotropy, the spin-wave dispersion relation in Tb exhibits an energy gap, Δ , at zero wave vector. This energy gap may easily be calculated by using the expansion in spin deviation operators of the Racah operators introduced in I [Eqs. (16) and (17)]:

$$\Delta = \epsilon(0) = \{ [A(0) + B(0) + g\mu_B H \cos(\delta - \phi)] \times [A(0) - B(0) + g\mu_B H \cos(\delta - \phi)] \}^{1/2}, \quad (15)$$

where we shall define the following quantities:

$$A(0) \pm B(0) = P_0(\pm) - P_6(\pm) \cos 6\phi. \quad (16)$$

We then have

$$P_0(+)= -\frac{1}{J} \sum_l l(l+1) \Gamma_{l,0} V'_{l0} + 14C \frac{1}{J} \Gamma_{4,2} B_{42} + 36C \frac{1}{J} \Gamma_{6,2} B_{62} - 11A \frac{1}{J} \Gamma_{6,4} B_{64} + 2c_\gamma C^2 + c_\gamma A^2 + N_c g\mu_B M, \quad (17a)$$

$$P_6(+)= 6(1/J) \Gamma_{6,6} V_{66} + 3c_\gamma AC + \Delta M, \quad (17b)$$

$$P_0(-)= 4c_\gamma (C^2 + A^2) + N_\perp g\mu_B M, \quad (17c)$$

$$P_6(-)= 10c_\gamma AC + 36(1/J) \Gamma_{6,6} V_{66}. \quad (17d)$$

The parameter ΔM in (17b) which is defined as the difference between $P_6(+)$ and $\frac{1}{6} g\mu_B H_c$ was introduced by Lindgard¹⁰ and in the present approximations is given by

$$\Delta M = P_6(+)-\frac{1}{6} g\mu_B H_c = 7A \frac{1}{J} \Gamma_{4,2} B_{42} + 18A \frac{1}{J} \Gamma_{6,2} B_{62} - 22C \frac{1}{J} \Gamma_{6,4} B_{64}. \quad (18)$$

In (17) we have included the effect of the demagnetization field as deduced by Keffer.¹¹ N_c and

N_{\perp} are the demagnetization factors, respectively, in the c direction and in the basal plane perpendicular to the magnetization \vec{M} . The field which enters into (13) and (15) is then the internal field. $B_{66}^{(i)}$, which has been neglected, would have given rise to terms proportional to $\cos^2 6\phi$ in both $A(0) + B(0)$ and $A(0) - B(0)$.

If C and A are both zero, then $P_0(-) = 0$ (except for the demagnetization contribution) and $P_6(-) = g\mu_B H_c$, and in this case the second-order transition at $H = H_c$ (H parallel to a hard axis) is accompanied by a vanishing of the energy gap Δ . The γ -strain contributions, which prevent the uniform magnon mode from going soft, were first considered by Turov and Sharov,⁵ and, because only the static parts of the strains have been introduced, they called it the "frozen-lattice" approximation. The time dependence of the inhomogeneous parts of the strains in (6) may be expanded in phonon operators and, as such, give rise to magnon-phonon interaction.¹² The homogeneous strains are essentially classical quantities, which result from the vanishing of the natural vibration energy of the lattice. On this basis Jensen,¹³ Chow and Keffer,¹⁴ and Liu¹⁵ have shown that the presence of the phonons in the systems has negligible effect on the magnon energy gap. In an attempt to explain the observation of ferromagnetic resonances in Dy and Tb¹⁶ at much lower frequencies than expected, Cooper³ proposed a flexible- or free-lattice model, which was based on the free energy of the system. In this model and in the equivalent one suggested by Vigren and Liu¹⁷ the energy gap vanishes at $H = H_c$ even in the case where the γ strains are nonzero. The previous assumptions for the dynamics of the spin-lattice system have been demonstrated to be incorrect by the neutron-scattering experiment performed on Tb-10%-at.-Ho,¹⁸ and by the solution of the equations of motion¹³⁻¹⁵ (see also II). Although (when the phonons are introduced) the lattice is completely "free," the spins will perceive the lattice as being "frozen." This apparent paradox is explained by the finite mass of the ions or, completely equivalently, by the vanishing of the eigenfrequency of the lattice at zero wave vector; the lattice cannot respond to a uniform spin precession at finite frequency.

As discussed, the uniform mode does not go soft at the transition at $H = H_c$ if γ -strain contributions are present. Instead, it is predicted¹³⁻¹⁵ that the long-wavelength phonons corresponding to the γ strain go soft, in the sense that the sound velocity (ω_q/q) goes to zero. The phonons in question are the acoustic transverse phonons with propagation and polarization vectors both lying in the basal plane (parallel or perpendicular to

the magnetization). The soft-phonon behavior has been observed experimentally^{19,20} at the Jahn-Teller phase transition in various rare-earth salts which represent systems equivalent to the one considered. Preliminary ultrasonic measurements on Tb indicate a softening of the phonons at $H = H_c$.²¹ These measurements are continuing, and one of the purposes is to clarify further the behavior of the basal-plane anisotropy in Tb determined by the present work. The soft-mode behavior in the metals may be affected by the existence of two-ion exchange interactions.

Referring to the equilibrium conditions for the strains, Eq. (8), it appears that the terms in the general spin Hamiltonian (7) in I, for which λ is different from zero, account for the magnetoelastic contributions. However, as described in I [mechanism (v)], such terms may occur also because of the polarization and the spin-orbit coupling of the conduction electrons, which modify the susceptibility and thus the indirect exchange interaction. Depending on the signs of the λ terms which are not of magnetoelastic origin, they may either enhance or resist the softening of the phonons. From the experimental results in Tb we isolate a contribution to the basal-plane anisotropy which is tentatively explained by this mechanism (v). The sign of this term is such as to enhance the softening of the transverse-phonon mode. The sound velocity may then vanish at a field smaller than the critical field, suggesting a structural change of the crystal at this field. See *Note added in proof*.

The introduction of two-ion interactions, as considered in I, still allows the energy gap to be written in the form given by (15) and (16), if terms in Eqs. (22) and (23) of I for which $\mu + m + m'$ is greater than 6 are neglected. Two-ion couplings for which $\lambda = 0$ may contribute to all the energy-gap parameters, $P_i(\pm)$, with the exception of $P_0(-)$, for which $m + m'$ in Eq. (23) of I is equal to zero. An explicit calculation of possible magnetoelastic contributions ($\lambda \neq 0$) to the energy gap shows that the γ -strain terms appearing in $g\mu_B H_c$, $P_0(-)$, and $P_6(-)$ can still be written in terms of C and A as given by (14), (17c), and (17d), where C and A defined by (9) include the single-ion contributions (10) as well as two-ion contributions. In this context we mention that "optical" strain contributions can be neglected because of the vanishing of the electric dipole moment of the ions [see the mechanisms (vi) and (vii) in I] and of the acoustic-optical coupling at $q = 0$, as discussed in II. Then within a linear theory the strains of the two hcp sublattices will have the same signs, and only "acoustic" strains are present.

In general it is not possible to distinguish between single-ion and two-ion contributions to the energy gap or to the static magnetic anisotropy. Only the strain-independent two-ion terms discussed above, for which λ is nonzero, may show up as differences between the energy-gap parameters and the corresponding ones obtained from macroscopic measurements. Torque or magnetization measurements are in most cases interpreted in terms of the single-ion crystal-field parameters of the undistorted lattice, Eq. (1). The magnetic anisotropy energy is assumed to depend on θ and ϕ in the following way²²:

$$F_A(\theta, \phi) = K_2 P_2^0(\cos\theta) + K_4 P_4^0(\cos\theta) + K_6 P_6^0(\cos\theta) + K_6^s \sin^6\theta \cos 6\phi, \quad (19)$$

where $P_l^m(\cos\theta)$ are the Legendre polynomials. Because of the strong axial anisotropy in Tb (and Dy) it is possible to compare the effective parameters defined by Eq. (19) with those derived from a more general (and realistic) Hamiltonian including terms whose angular dependences differ from those introduced in (19). In a torque or magnetization experiment on Tb or Dy the magnetic moments are pulled only a few degrees out of the basal plane towards the c axis, and (19) can be approximated by the expansion

$$F_A(\theta, \phi) = F_A\left(\frac{\pi}{2}, \phi\right) + \frac{1}{2!} F_A^{(2)}\left(\frac{\pi}{2}, \phi\right) \delta\theta^2 + \frac{1}{4!} F_A^{(4)}\left(\frac{\pi}{2}, \phi\right) \delta\theta^4, \quad (20)$$

where $\delta\theta = \theta - \frac{1}{2}\pi$ and

$$F_A^{(2)}\left(\frac{\pi}{2}, \phi\right) = \left(\frac{\partial^2 F_A(\theta, \phi)}{\partial \theta^2}\right)_{\theta=\pi/2} = 3K_2 - \frac{15}{2}K_4 + \frac{105}{8}K_6 - 6K_6^s \cos 6\phi. \quad (21)$$

The true anisotropy energy may be written as a similar power expansion in $\delta\theta$, and the effective axial anisotropy parameters determined by experiments, K_l^m , may be considered as a measure of the second (and fourth) derivative of the free energy as given by (21). $F_A^{(2)}(\frac{1}{2}\pi, \phi)$ will represent the second derivative of the actual anisotropy also in cases where K_6 or K_4 and K_6^s have been neglected in the interpretation of the anisotropy measurements.

As considered in I, the spin-wave energy gap is closely related to the second derivatives of the free energy³ [Eqs. (24) and (25) of I]. If we neglect the terms in the general Hamiltonian (7) of I proportional to $\cos 12\phi$ and $\cos 18\phi$ ($p \neq 0, 1$) and also the terms for which λ is different from

zero but which do not contribute to the elastic energy, we obtain the following expressions for the energy-gap parameters in terms of macroscopic parameters:

$$A(0) + B(0) = (1/NJ) F_A^{(2)}(\frac{1}{2}\pi, \phi) + \frac{1}{4} c_\epsilon H_0^2 + N_c g \mu_B M, \quad (22a)$$

$$A(0) - B(0) = 4c_\gamma (C^2 + A^2) - [36(1/NJ)K_6^s - 8c_\gamma AC] \cos 6\phi + N_\perp g \mu_B M, \quad (22b)$$

where the basal-plane anisotropy is simply related to the critical field

$$K_6^s = \frac{1}{36} NJ g \mu_B H_c. \quad (23)$$

In distinction to the α and γ strains, the first derivatives of the ϵ strains with respect to θ are different from zero at $\theta = \frac{1}{2}\pi$, which is the reason for the presence of ϵ -strain contributions to (22a). H_0 is considered to be an effective magnetostriction coefficient given by

$$H_0 = \frac{2}{Jc_\epsilon} \sum_l [l(l+2)]^{1/2} \Gamma_{l+1,1} B_{l1} \quad (24)$$

when two-ion contributions and B_{65} in (6) are neglected. The macroscopic expression for the energy gap, (22), is quite general because of the inclusion of two-ion interactions. The terms which give rise to 12ϕ and 18ϕ dependences are presumably small and are neglected. They would have modified the equilibrium equation determining ϕ , (13), and hence the magnitude of the critical field, and the transition at this field could be of first order.

The two-ion λ terms, which are not of magnetoelastic origin, are not necessarily negligible and may lead to differences between the macroscopic energy-gap parameters, as given by (22), and the actual (microscopic) energy-gap parameters. Defining

$$\delta_i(\pm) = [P_i(\pm)]_{\text{micr.}} - [P_i(\pm)]_{\text{macr.}}, \quad i = 0, 6, \quad (25)$$

we have, e.g.,

$$\delta_6(-) = \sum_{\lambda\mu} \sum_{im} \sum_{i'm'} \frac{1}{J} K_{\lambda i i'}^{\mu m m'}(0) \mu (12 - \mu) \times \Gamma_{\lambda, \mu} \Gamma_{i, m} \Gamma_{i', m'}, \quad (26)$$

using the notation introduced in I ($\mu + m + m' = 6$). The corresponding expressions for the other differences may easily be obtained from the energy-gap expressions deduced in I [(21)–(25)]. As quoted in I [mechanism (iv)] the indirect exchange interaction perturbs the energy gap so to give rise to a relative shift of the order of 2.5%, which will also appear in the differences $\delta_i(\pm)$. At low temperatures we may have additional contributions

to $\delta_i(\pm)$ from the zero-point motion of the magnetic moments and of the ions. The zero-point effects due to magnon-magnon interactions can give rise to a deviation between static and dynamic measurements. The importance of these contributions increases with the strength of the anisotropy and with the rank l of the tensor spin operators considered. In the Hartree-Fock calculation by Lindgård and Danielsen,²³ in which two-ion anisotropy has been neglected, the contributions to $\delta_i(\pm)$ in Tb arising from the magnon-magnon interactions are found to be quite small, except for the contributions to $\delta_6(-)$. The results by Lindgård and Danielsen do not seem to confirm the proposal by Egami²⁴ of a strong ϕ dependence of the basal-plane anisotropy in Dy. The two-magnon-one-phonon scattering processes¹³ may also give rise to zero-point contributions (see II); however, they are probably not as important as, and may hardly be distinguished from, those due to magnon-magnon interactions.

The equations above, which describe the behavior of the spin system at zero temperature, may be generalized to the case of finite temperature by the procedure outlined in I, (31)–(35). The deviation of the relative magnetization σ [Eq. (31) of I] from unity may be taken into account by replacing J with σJ in all formulas. In Eqs. (17) and (22) the magnetization M is replaced by $M(0)\sigma^2/\sigma = M(T)$. The strong anisotropy of the basal-plane ferromagnets Tb and Dy may in addition to a modification of the Callen and Callen theory² [Eq. (33) of I], introduce deviations from the simple spin-wave renormalization theory of Cooper,³ which should be of an appreciable magnitude in the case of $P_6(-)$ according to the results obtained by Lindgård and Danielsen.²³

III. ENERGY-GAP MEASUREMENTS

The spin-wave energy gap in Tb at zero wave vector was studied by inelastic neutron scattering. Because of the finite energy of the long-wavelength magnons (~ 1 – 2 meV), the Bragg reflection does not disturb the observation of the neutrons scattered by the magnons at zero wave vector. In Fig. 1 is shown the neutron groups obtained at $q=0$ (the scattering vector equals a reciprocal-lattice vector) in zero magnetic field and at maximum field applied in the hard direction of Tb at 40 K. The sample was a monocrystalline disc with a diameter of about 14 mm and a thickness of about 5 mm and with the c axis normal to the faces. From the saturation magnetization of Tb,²⁵ the demagnetization field normal to the c axis in the sample is deduced to be $N_{\perp}M(T) = \sigma \times 6.65$ kOe. The energy gap as a function of magnetic field ap-

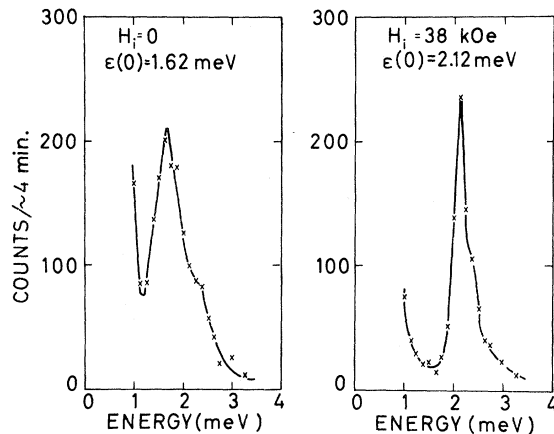


FIG. 1. Example of neutron groups obtained in Tb at zero wave vector. The scattering vector is along the c axis and equal to $4\pi/c$. The groups are measured at (a) 40 K in zero field and (b) an internal field equal to 38 kOe applied in a hard direction.

plied along the easy and hard directions in the basal plane was measured in a temperature interval ranging from 4.2 to 130 K. In this temperature range, which corresponds to a relative magnetization between 1 and 0.8, the field dependence of the magnetization is quite well described by the molecular-field result [Eq. (34) of I] as indicated by the magnetization measurements.²⁵ Further, we have calculated the forced magnetostriction $d(2C+A)/dH$ based on the magnetostriction theory of Callen and Callen² by using the value obtained from Eq. (34) of I: $d\sigma/dH = (1-\sigma) 0.0027$ kOe⁻¹, and found a fair agreement with the experimental results of Rhyne and Legvold⁹ for $\sigma > 0.8$ (Fig. 2).

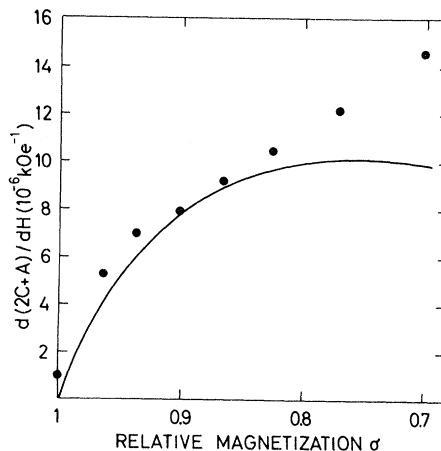


FIG. 2. Forced magnetostriction $d(2C+A)/dH$ in Tb determined by experiments (Ref. 9) and calculated by using the magnetostriction theory of Callen and Callen (Ref. 2). The deviation at high temperatures ($\sigma < 0.8$) may be due to contributions which are not linear in field.

The experimental procedure and the treatment of the results follow the lines discussed in I. The interpretation is facilitated by the vanishing of the direct coupling of magnons and phonons at zero wave vector (II). The effective g value introduced in I, (30), has not been used in the present treatment, partly because of the smallness of the correction and partly because it is expected to be cancelled by opposite contributions at $q=0$ arising from mechanism (iv) in I.

A selection of the experimental results for the energy gap at $q=0$ is shown in Fig. 3. They are qualitatively similar to earlier measurements¹⁸ on Tb-10%-at.-Ho, but they are made with considerably greater precision, and in this experiment the effect of the field dependence of σ is taken into account. This correction introduces changes of the magnetization exponents connected with the $A(0)\pm B(0)$ parameters, which are of the order of ± 1 . In the Tb-10%-at.-Ho experiment the number of independent parameters was reduced by adopting a particular model corresponding to Eqs. (14)–(18) if ΔM is neglected; an attempt was made to isolate the magnetoelastic contribution to the critical field, Eq. (14), by neglecting the possibility of a difference $\delta_6(-)$ between the macroscopic and microscopic parameters. The greater precision of the present experimental results for pure Tb allow us to avoid such assumptions. The only assumption made is that terms proportional to $\cos 12\phi$ and $\cos 18\phi$ can be neglected. The parameters which are deduced from the energy-gap measurements are then the four $P_i(\pm)$ defined by Eqs. (15) and (16)

and the critical field, H_c . The abrupt changes of the field dependences of Δ^2 when the field is applied in a hard direction (Fig. 3) serve as a well-defined determination of the critical field as a function of temperature. The field dependence of ϕ is then obtained from Eq. (13). The σ dependence of $P_i(\pm)$ defined by

$$P_i(\pm) \propto \sigma^{\gamma_i(\pm)} \quad (27)$$

implies corrections to the energy-gap expression, (15) and (16), as given by

$$\begin{aligned} A(0)\pm B(0) &= P_0(\pm) - P_6(\pm) \cos 6\phi \\ &+ \frac{1}{\sigma} [\gamma_0(\pm)P_0(\pm) - \gamma_6(\pm)P_6(\pm) \cos 6\phi] \\ &\times \frac{d\sigma}{dH} (H-H_a), \end{aligned} \quad (28)$$

where $H_a=0$ when the field is applied in an easy direction, and when applying the field along a hard axis $H_a=H$ for $H < H_c$ and $H_a=H_c$ for $H > H_c$ ($d\sigma/dH$ is assumed to be zero as long as $H < H_c$).

The energy-gap parameters $P_i(\pm)$ shown in Fig. 4 were deduced from a least-squares fitting of the experimental results to the Eqs. (13), (15), and (28). The σ dependences of $P_i(\pm)$, which were obtained in a self-consistent manner, show no deviations from the simple power-law behavior assumed by Eq. (27). The parameters so deduced, together with their uncertainties, are given in Table I, and it is apparent that $P_6(+)$ differs substantially from $\frac{1}{6} g_{\text{eff}} \mu_B H_c$, implying that ΔM is different from zero. The necessity for including ΔM may be seen directly in the measurements

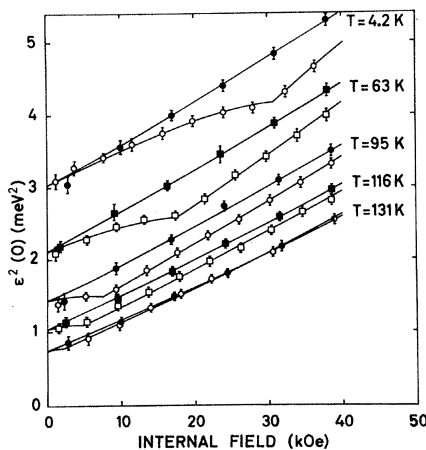


FIG. 3. Dependence of the square of the magnon energy gap on internal magnetic field in Tb. Open symbols represent results for the field in the hard direction, and closed the easy direction. The full lines are least-squares fits of the energy-gap expression, given in the text, to the experimental results.

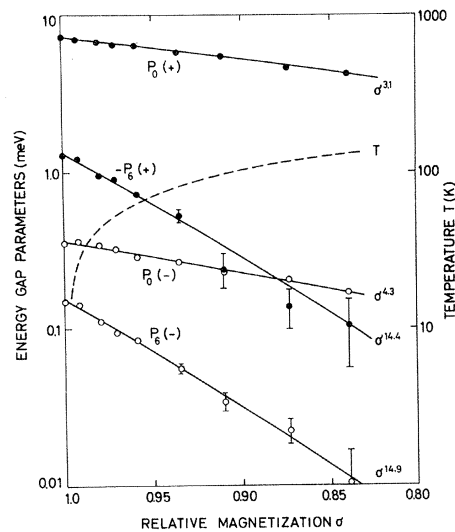


FIG. 4. Anisotropy parameters $P_i(\pm)$ in Tb as a function of magnetization, deduced from the results of Fig. 3 and similar measurements at different temperatures.

of Fig. 3, since it is responsible for the difference between the slopes of the straight lines obtained for fields applied in the easy and hard directions. The appropriate g value for the macroscopic hexagonal anisotropy is the effective value defined by Eq. (30) of I as used in Table I, $g_{\text{eff}} \mu_B H_c$.

IV. COMPARISON WITH STATIC EXPERIMENTS

Deviations from the simple spin-wave renormalization theory of Cooper³ or the presence of two-ion λ terms, which are not of magnetoelastic origin, may be detected by a comparison of the energy-gap parameters $P_i(\pm)$ with the corresponding macroscopic parameters deduced from static measurements²² as given by Eq. (22). The temperature dependence of a parameter deduced from static experiments is usually fitted to the temperature law predicted by Callen and Callen² for the (single-ion) term of lowest rank which contributes to the parameter in question. The fits which are obtained based on these assumptions may be quite good, as is the case, e.g., for C and A in Tb,⁹ but deviations occur, especially in the low-temperature region which we are considering ($\sigma > 0.8$). At low temperatures the terms of higher rank may contribute appreciably to the σ dependence, and the applicability of the Callen-Callen theory in the case of a highly anisotropic system is questionable. Because of these limitations we have fitted a simple power-law σ dependence to the experimental results obtained for the magnetostriction parameters C , A ,⁹ and H_0 ,^{26,27} in the temperature interval corresponding to $\sigma > 0.8$. The results are given in Table II. The standard deviations, which are also given, are deduced from the statistical scatter of the experimental results and do not include systema-

TABLE I. Anisotropy parameters $P_i(\pm)$ and $g_{\text{eff}} \mu_B H_c$ for Tb derived from the energy-gap measurements as described in the text. The zero-temperature values of the parameters are given in meV, whereas the magnetization exponents, which describe the temperature dependence of the parameters, are pure numbers. Parameters independent of the actual shape of the crystal may be obtained by subtracting the dipolar contributions $N_c g \mu_B M$ and $N_{\perp} g \mu_B M$ from $P_0(+)$ and $P_0(-)$, respectively.

Anisotropy parameter	Exponent
$P_0(+)$	7.22 ± 0.07
$P_6(+)$	-1.34 ± 0.04
$P_0(-)$	0.361 ± 0.008
$P_6(-)$	0.154 ± 0.003
$g_{\text{eff}} \mu_B H_c$	0.290 ± 0.005
$N_c g \mu_B M$	1
$N_{\perp} g \mu_B M$	1

tic experimental errors. The elastic constants for Tb have been measured by Palmer *et al.*²⁸ as function of temperature and in a field of 25 kOe applied along an easy axis, by which domain effects are eliminated. c_{66} and hence c_{γ} is strongly influenced by magnon-phonon interactions,^{12,13} and we use a value which is $(7 \pm 4)\%$ greater than the one obtained from experiment. From the magnetostriction coefficients and the elastic constants, the magnetoelastic coupling parameters, $\sigma c_{\gamma} C$, etc., may be deduced, and they are also given in Table II. Notice that we have included implicitly a factor $1/\sigma$ in the definitions of c_{γ} and c_{ϵ} following from the factor $1/J$ in Eq. (5). We remark that if a system is magnetoelastically isotropic [$\mathcal{H}_{\text{cf-e}}$, (6), independent of a coordinate transformation] then the parameters in (6) are related. Among these relations are $A=0$ and $\sigma c_{\epsilon} H_0 = 4\sigma c_{\gamma} C$, and it is interesting to notice that the last relation is fulfilled almost exactly in Tb. If terms of higher rank than $l=2$ for C and H_0 and $l=4$ for A in the Eqs. (10) and (24) and two-ion magnetoelastic contributions are neglected then the Callen-Callen theory predicts a renormalization of $\sigma c_{\gamma} C$ and $\sigma c_{\epsilon} H_0$ proportional to σ^3 and of $\sigma c_{\gamma} A$ proportional to σ^{10} . The low-temperature theory of Lindgård and Danielsen²³ predicts somewhat higher exponents, 3.4 and 14.6 for $\sigma c_{\gamma} C$ and $\sigma c_{\gamma} A$, respectively. The experimental exponents given in Table II, which are smaller than those suggested by the theories, may indicate the importance of two-ion contributions.

The magnetostriction coefficient H_0 is derived partly from the experiments of DeSavage and Clark²⁶ and Du Plessis,²⁷ which were performed in the paramagnetic phase, and partly from the amplitude of the magnon-phonon interaction at low temperatures as described in II. C and A and the α strains were measured by Rhyne and Legvold.⁹ $B_{66}^{(1)}$ in Eq. (6) and the corresponding

TABLE II. γ - and ϵ -magnetostriction parameters of Tb. C and A are obtained from Ref. 9 and H_0 is deduced in II. The magnetoelastic coupling parameters, $\sigma c_{\gamma} C$ etc., given in units of meV, are obtained by using the measured elastic constants (from Ref. 27), as described in the text. The exponents give the σ dependence of the parameters for $\sigma > 0.8$.

Magnetostriction parameter	Exponent
$C \times 10^3$	4.18 ± 0.02
$A \times 10^3$	2.11 ± 0.02
$H_0 \times 10^3$	18.5 ± 2
$\sigma c_{\gamma} C$	15.0 ± 0.6
$\sigma c_{\gamma} A$	7.6 ± 0.3
$\sigma c_{\epsilon} H_0$	62 ± 7

two-ion terms introduce a ϕ dependence of the α strains. In the interpretation of their results, Rhyne and Legvold neglected this possibility; these terms would then appear as a difference between C deduced from b -axis data and from a -axis data, whereas A would be unaffected. In their experiment Rhyne and Legvold⁹ detected such a difference for C , which we interpret as arising from a ϕ dependence of $\epsilon^{\alpha,i}$, with a magnitude of about $0.15 \times 10^{-3} \times \sigma^{7.3}$. The appropriate C value is the mean of the a - and b -axis data which is the one given in Table II. The neglect of a ϕ -dependent α strain of this magnitude will appear in $\delta_0(-)$ in our results with a contribution equal to -3×10^{-4} meV, which is entirely negligible. Bartholin *et al.*²⁹ have isolated the contributions to the α strains from the (isotropic) exchange interaction by studying the change of the Néel temperature with uniaxial pressure. Combining these measurements with the α -strain measurements,⁹ we deduce an α -strain contribution to $P_0(+)$ equal to $-0.43 \times \sigma^{1.4}$ meV.

The magnetic anisotropy parameters K_i^m , defined by Eq. (19), have been measured by torque and magnetization experiments. Rhyne and Clark³⁰ have determined K_2 in the easy direction by torque measurements and deduced K_6^6 from the magnetostriction measurements.⁹ Feron *et al.*³¹ have obtained K_2 , K_4 , and K_6^6 by magnetization measurements, where K_2 and K_4 are the effective anisotropy parameters in the easy direction. K_6^6 determined in these experiments should be directly comparable with the critical field H_c obtained in the present experiment through the relation (23). As shown in Fig. 5, the critical fields deduced by the different techniques agree

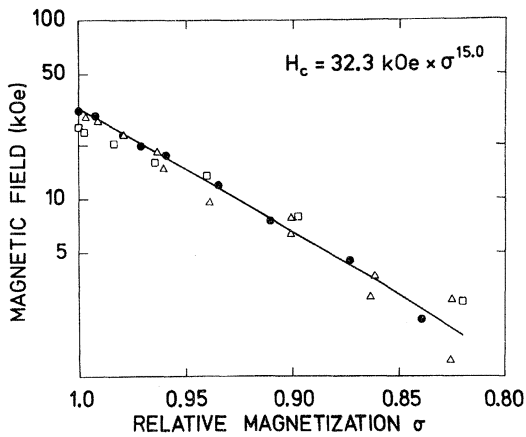


FIG. 5. Critical field H_c as function of magnetization. The closed circles are the results obtained by the present experiments on Tb. The open symbols are the results of the measurements by Rhyne and Clark (Δ , Ref. 30) and by Feron *et al.* (\square , Ref. 31).

satisfactorily. From the experimental result for the magnetic anisotropy parameters^{30,31} and for the ϵ strain (Table II) we have calculated the macroscopic value for $P_0(+)+P_6(+)$ according to the Eqs. (21) and (22a). $P_0(+)+P_6(+)$ is equal to $A(0)+B(0)$ when the magnetization is along an easy axis. The comparison is shown in Fig. 6. The large absolute uncertainties of the static anisotropy parameters (of the order of 25%) may disguise a difference of the order $\delta_0(+)+\delta_6(+)\approx 0.4 \pm 1.0$ meV, but the similarities of the σ dependence suggest that the difference is probably quite small.

The static expression for $A(0)-B(0)$ involves only the γ -strain contributions and the critical field as given by Eq. (22b). In Table III we compare the static and dynamic values for $P_i(-)$. The agreement between the two values for $P_0(-)$ is extremely good, with respect to both the absolute magnitude at zero temperature and the temperature dependence. In the case of $P_6(-)$ we obtain a significant difference $\delta_6(-)$. To elucidate this difference further we have subtracted the (static) magnetoelastic contribution $10c_\gamma AC$ from both the microscopic and macroscopic results for $P_6(-)$:

$$(P_{66})_{\text{micr.}} = P_6(-) - 10c_\gamma AC, \quad (29a)$$

$$(P_{66})_{\text{macr.}} = g_{\text{eff}} \mu_B H_c - 8c_\gamma AC - 10c_\gamma AC. \quad (29b)$$

The ratio between the dynamic and static hexagonal anisotropies of the unstrained lattice is close to 2 and is practically independent of temperature. Note that this part of the static anisotropy $(P_{66})_{\text{macr.}}$ has the opposite sign to the total static basal-plane anisotropy K_6^6 , and that it renormalizes quite slowly with temperature, as $\sim \sigma^6$.

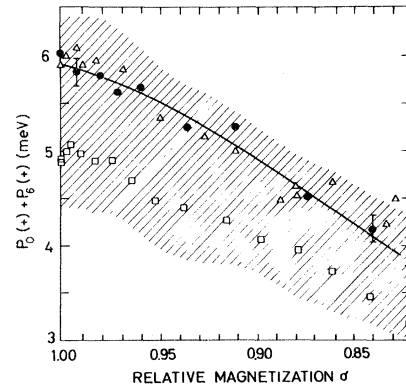


FIG. 6. Comparison of the energy-gap parameter $A(0)+B(0)$ in the easy direction of Tb (closed circles) with the static values deduced from the magnetic anisotropy measurements as described in the text (Δ from Ref. 30 and \square from Ref. 31). The cross-hatched area shows the probable region in which the macroscopic parameter lies when combining the two different anisotropy measurements.

TABLE III. Comparison of static and dynamic energy-gap parameters. The microscopic (dynamic) anisotropy parameters are from Table I, and the macroscopic parameters are deduced from the parameters given in Tables I and II according to Eq. (22b).

Anisotropy parameter		Exponent
$P_0(-)$	{ dyn. 0.361 ± 0.008	4.3 ± 0.3
	{ sta. 0.367 ± 0.011	4.2 ± 0.13
$\delta_0(-)$	$\sim 0 \pm 0.014$...
$P_6(-)$	{ dyn. 0.154 ± 0.003	14.9 ± 0.8
	{ sta. $\sim 0 \pm 0.03$...
$\delta_6(-)$	0.126 ± 0.010	5.9 ± 0.3
P_{66}	{ dyn. -0.167 ± 0.013	5.6 ± 0.5
	{ sta. -0.292 ± 0.024	5.8 ± 0.4

V. DISCUSSION

From the measurements of the field dependence of the energy gap at zero wave vector in the spin-wave spectrum presented in this paper, some of which have been published earlier,³² we deduce a strong axial anisotropy in Tb, which has also been observed by torque³⁰ and magnetization³¹ measurements. Further, we find that the axial anisotropy depends sensitively on the orientation of the magnetic moments in the basal plane. The large value for $P_6(+)$ which we obtain can hardly be explained within a single-ion model for the anisotropy, Eqs. (17) and (18), as $\Delta M = P_6(+)$ $-\frac{1}{8}g_{\text{eff}}\mu_B H_c = -1.39 \times \sigma^{14.3}$ meV is an order of magnitude larger than the γ -strain terms in $P_i(-)$. If C , A , and ΔM were all of magnetoelastic single-ion origin, then the magnitude of ΔM would require C and A to be differences between terms which were 10 times larger and with different σ dependences. Most of the contributions to ΔM are presumably of two-ion origin. By the inclusion of two-ion interactions a general expression for the energy gap was deduced in I [Eqs. (21)–(23)]. Two types of two-ion interactions may contribute to $P_6(+)$, those for which $l+m$ and $l'+m'$ are both even, and those for which they are both odd. However, when $\frac{1}{8}g_{\text{eff}}\mu_B H_c$ is subtracted from $P_6(+)$, the remaining part ΔM is mostly composed of two-ion contributions for which $l+m$ and $l'+m'$ are both odd; these are the same interactions which give rise to the \vec{q} -dependent anisotropy, $\mathcal{C}(\vec{q})$ derived in I. We found in I that $\mathcal{C}(\vec{q})$ gives rise to an interplanar contribution to $P_6(+)$ equal to -1.6 meV at zero temperature. On the basis of this strong correlation between $\mathcal{C}(\vec{q})$ and ΔM , both with respect to their magnitudes and their σ dependences, combined with the arguments above we conclude that ΔM is of two-ion origin. A possible strain dependence of these couplings ($\lambda \neq 0$) will not affect the γ or α strains or the difference

$\delta_6(+)$.

In I anisotropic two-ion couplings were found to be important in Tb, giving rise to \vec{q} -dependent anisotropy, and there is therefore the possibility of large two-ion contributions to the magnetic anisotropy at $q=0$. The evidence for the two-ion origin of ΔM is convincing. The differentiation between single-ion and two-ion contributions to $P_0(+)$ is more uncertain. An attempt may be based on the studies by Høg and Touborg,³³ who have determined the crystal-field anisotropy by magnetization measurements on single-crystal alloys of rare-earth metals diluted in Y, Lu, and Sc, and the equivalent torque measurements on dilute alloys of rare-earth ions in Gd by Chikazumi *et al.*³⁴ Asada³⁵ has later corrected the Gd results for the effect of finite concentration of the rare-earth impurities. The remarkable consistency of the crystal-field parameters obtained for a rare-earth ion, when placed in the different systems, supports a use of these parameters as a measure of the single-ion anisotropy present in the pure metal. The results of Høg and Touborg³³ and of Asada³⁵ both suggest a single-ion contribution to the axial anisotropy $P_0(+)$ in Tb of the order of 2 meV, leaving 5 meV as being of two-ion origin. The single-ion magnetoelastic part of $P_0(+)$ is probably small, as shown by the estimated α -strain contribution which is compensated almost exactly by $c_\gamma(2C^2 + A^2)$ and the dipolar term. The \vec{q} -dependent axial anisotropy in Tb, $\mathcal{K}(\vec{q})$ in I, indicates that part of the interplanar contributions to $P_0(+)$ is negative. Such negative contributions may be connected to two-ion couplings of low rank which would be consistent with the tendency found by Boutron,³⁶ who considered the two-ion couplings for which $l=l'=1$. That the total two-ion axial anisotropy at $q=0$ is found to be positive indicates the importance of couplings of higher rank.

The only couplings which appear in $P_0(-)$ are those for which μ (and hence λ) are different from zero, Eq. (23) of I. By expressing $P_0(-)$, (17c), in terms of C and A , which are defined by Eq. (9), we have included all contributions of magnetoelastic origin. Polarization and spin-orbit coupling effects on the susceptibility of the conduction electrons may introduce terms for which λ is nonzero, when combined with the indirect $s-f$ exchange interaction, $J_{sf}(0) \approx 8$ meV in Tb. From the order-of-magnitude estimate in I [mechanism (v)] we expect contributions to the energy-gap parameters $P_i(-)$ of the order of $(m+m')^2$ times 8×10^{-3} meV. Two-ion terms arising from this mechanism, for which μ is different from zero, would appear in $\delta_0(-)$ and $\delta_6(-)$, Eq. (26). There is no indication of such a contribution to $\delta_0(-)$, whereas $\delta_6(-)$ is different from zero, as appears

from Table III. In fact, terms for which μ is equal to 1 or 2 would account for the factor of 2 between the dynamic and static values of P_{66} , and a term like $K_{222}^{222}(0)$ would, according to the simple renormalization theory [Eqs. (32) and (33) of I], be proportional to $\sigma^3 - \sigma^{12}$, which is fairly close to the observed σ^6 dependence. A two-ion contribution to $P_6(-)$ of this order of magnitude is consistent with the estimated interplanar term arising from the \vec{q} -dependent anisotropy, $\mathfrak{D}(\vec{q})$ in I [$\approx P_6(-)$].

The magnon-magnon interaction^{23,24} may introduce zero-point deviations between static and dynamic variables. In the theory of Lindgård and Danielsen²³ two-ion anisotropy is neglected, and they predict a detectable deviation only in the case of the sixfold basal-plane anisotropy V_{66} , for which the dynamic value should be about half the static one. This is in accordance with the observed behavior of P_{66} in Tb, but introduces in Dy an effect which is opposite in sign to the one deduced from experiments.³⁷ Further, the σ -dependence of P_{66} expected from the theory of Lindgård and Danielsen is inconsistent with the experimental results. The low-temperature theory predicts an exponent for the dynamic V_{66} which is about twice the value of 20 given by the simple $\frac{1}{2}l(l+1) - 1$ law. The small exponent observed for P_{66} allows us to draw the conclusion that the most important contributions to P_{66} are of two-ion origin. A two-ion origin of P_{66} or the small σ exponent obtained further indicates that the zero-point difference between the dynamic and the static P_{66} ($\lambda + l + l' = 6$) should be considerably smaller than the one deduced²³ for V_{66} ($l = 6$). This leads us to propose mechanism (v) in I for the observed difference $\delta_6(-)$ as a more probable explanation than the magnon-magnon interaction.

The possibility of several types of contributions to the deduced parameters does not allow any definite conclusions about deviations from the Callen-Callen theory,² generalized to the dynamic case by Cooper,³ which is predicted^{23,24} for a strongly anisotropic basal-plane ferromagnet. For this purpose Dy may serve as a better candidate than Tb, because of the presence of a large basal-plane anisotropy in Dy. Nicklow and Wakabayashi³⁷ have observed an energy gap in Dy equal to 3.2 meV at zero temperature by neutron scattering, whereas the value obtained from the static measurements^{22,31} is 2.6 ± 0.4 meV. The large difference suggested by these numbers deserves further study. By similar measurements of the field dependence of the energy gap in Dy a distinction between the $\delta_i(\pm)$ may be obtained, together with a more reliable determination of the critical field (~ 135 kOe at zero temperature). A ϕ de-

pendence of the susceptibility of the conduction electrons which may explain the peculiar behavior of P_{66} in Tb may not account for the large difference of the order of 0.6 meV in Dy. The softening of the velocity of transverse sound waves propagating in the basal plane at fields close to the critical field is presumably not affected by the magnon-magnon interaction (only dynamic parameters are involved), whereas the presence of strain-independent λ terms will influence the critical behavior. Ultrasonic studies of the transition at the critical field in Tb and Dy could clarify the origin of the discrepancies between the static and the dynamic values for the energy gaps. See *Note added in proof*.

VI. SUMMARY

In the three papers I, II, and III we have presented a detailed experimental and theoretical analysis of the magnetic excitations propagating in the c direction of Tb. The ground state of the ionic moments in Tb,^{25,38} which are ferromagnetically ordered at low temperatures, is presumably close being a pure $J_z = J = 6$ state; so the spin-wave approach is applicable. The description of the spin waves propagating in the c direction of a hexagonal solid is especially simple because the effective Hamiltonian is close to being invariant with respect to a rotation of the magnetization vector around the c axis by an angle which is a multiple of $\frac{1}{3}\pi$. If the c axis is considered to be an effective sixfold axis, then the absence of acoustic-optical couplings implies that the double-zone representation for the hcp lattice is valid. The direct mixing of spin space variables accomplished by the spin-orbit coupling of the conduction electrons causes a lowering of the effective symmetry. The spin-orbit coupling introduces a further complication, as it gives rise to a deviation between the direction of magnetization and the direction in which the conduction electrons are polarized. This deviation may introduce couplings violating the selection rules for a simple ferromagnet, as is the case for the acoustic-optical magnon-phonon interaction observed in Tb.

A general dispersion relation for spin waves propagating in the c direction of a basal-plane ferromagnet was derived. The different forces acting on the ionic magnetic moments may be divided into the three classes: single-ion, two-ion, and polarization-dependent two-ion spin interactions. Three- or many-ion interactions can be decoupled into effective two-ion interactions. The positional dependence of all three types of coupling appears as static magnetostrictive contributions to the magnon energies and as a dynamic inter-

action between the magnons and the lattice vibrations.

Different aspects of the magnetic anisotropy in Tb were studied by measuring the change of the magnon dispersion relation when an external magnetic field was applied along a symmetry direction in the basal plane. By such an external perturbation of the magnon spectrum it is possible to determine the two Bogoliubov energy components $A(\vec{q}) + B(\vec{q})$ and $A(\vec{q}) - B(\vec{q})$. If $B(\vec{q})$ is nonzero, then the total magnetization, which is the sum of the z components of the ionic moments, does not commute with the spin-wave Hamiltonian. $B(\vec{q})$ vanishes identically for a c -axis magnet, whereas deviations from the fully aligned ground state assumed in a spin-wave approximation may be important in a basal-plane magnet.^{23,24} For a c -axis magnet, only terms for which $\mu = 0$ and $m = -m' = 1$ in Eq. (7) of I can contribute to the dispersion of the c -axis magnons, and $A(\vec{q}) + B(\vec{q})$ and $A(\vec{q}) - B(\vec{q})$ are degenerate [$B(\vec{q}) = 0$]. The information about magnetic anisotropy which may be obtained from the dispersion of the magnons in this spin configuration is thus rather limited. The basal-plane spin configuration which occurs in Tb and Dy is more informative, and the possibility of changing the orientation of the moments within the basal plane of Tb has led to the observation of spin couplings of high rank. $\lambda + l + l' \geq 6$ for the terms which contribute to the ϕ -dependent anisotropy, $P_6(\pm)$, and $\mathcal{C}(\vec{q})$ and $\mathcal{D}(\vec{q})$ derived in I.

In II we isolated the effects of the direct coupling between magnons and transverse phonons at finite wave vector. Within certain limitations, we determined explicitly the terms in the energy gap at zero wave vector arising from magnetoelastic coupling (ΔM may include magnetostrictive two-ion contributions). By this procedure we accounted for most of the effects of coupling between the spin system and the lattice. Magnetostrictive distortions of the lattice may enhance existing two-ion anisotropy, and this effect may in principle be investigated by applying a uniaxial pressure.

By the determination of $A(\vec{q}) \pm B(\vec{q})$ at both zero and finite wave vector we have separated the constant and the \vec{q} -dependent anisotropy. The results indicate that all three types of spin couplings contribute to the constant anisotropy. The single- and two-ion contributions seem to be of comparable importance, and the comparison between the static and dynamic anisotropy suggests the presence of a small polarization-dependent term. The \vec{q} dependence of the unperturbed energy parameters $A(\vec{q}) \pm B(\vec{q})$ reflects intrinsic properties of the spin system and is due to two- (and many-) ion couplings. The different kinds of spin interactions present in Tb can be listed according to their

relative importance on the magnon energies at zero temperature as follows: (i) Heisenberg interaction, ~ 7 meV; (ii) two-ion anisotropy, ~ 3 meV; (iii) single-ion anisotropy, ~ 3 meV; (iv) magnetoelastic coupling, ~ 0.5 meV; (v) polarization-dependent two-ion anisotropy, ~ 0.2 meV. The determination of the different contributions to the energy suffers from considerable uncertainty which is reflected in the typical energies listed above.

The behavior of the spin system in Tb is dominated by two-ion couplings between the ionic moments, (i) and (ii). In the heavy-rare-earth metals the electric multipole interactions [mechanism (vi) in I, l and $l' \neq 0$] are of minor importance in comparison with the indirect exchange interaction via the conduction electrons. The two-ion anisotropy which has been observed to be present in Tb, Dy, and Er is presumably due to the influence of mechanisms (i) and (ii), described in I, on the exchange interaction. A theoretical calculation of the indirect exchange interaction from first principles would be extremely complicated, as it requires a knowledge of the relativistic wave function of both the localized $4f$ electrons and the conduction electrons and a correct treatment of screening. Relativistic effects such as the spin-orbit coupling of the conduction electrons, (ii), may turn out to be as important as the Kaplan-Lyons terms, (i).

Utilizing the systematic behavior through the heavy-rare-earth series, the microscopic origin of magnetic anisotropy in these metals may be further elucidated experimentally. The behavior of the elementary excitations of a magnetically ordered metal is determined by certain linear combinations of general spin couplings which depend on the orientation of the ordered moments. When comparing the magnetic properties of the rare-earth metals the terms appearing in the linear combinations, $A(\vec{q}) \pm B(\vec{q})$, in identical spin configurations may scale differently according to the rank l and to the origin of the terms. A rough estimate of the scaling of the anisotropy energy E_A in the heavy-rare-earth metals due to orbital modifications ($\propto L$) of the exchange interaction ($\propto S$) is $E_A \propto LS = (2-g)(g-1)J^2$. This expression should not be taken too literally, as, e.g., the spin-orbit coupling, (ii), may give rise to two-ion anisotropy in Gd ($g=2$), as mentioned in I.

ACKNOWLEDGMENTS

The authors of the preceding three papers are grateful to A. R. Mackintosh, who participated in the early stages of the work, for valuable suggestions, stimulating interest, and a critical

reading of the manuscripts. Helpful discussions with R. J. Birgeneau, R. J. Elliott, P. A. Lindgård, O. Danielsen, P. Bak, and M. Nielsen are also gratefully acknowledged.

Note added in proof. The polarization-dependent two-ion coupling is most likely interpreted as a

dynamic effect which vanishes in the limit of zero energy. The behavior of the long-wavelength phonons (\approx zero energy) should be adequately described by the macroscopic anisotropy parameters [see a discussion by Jensen (to be published)].

-
- ¹W. P. Mason, *Phys. Rev.* **96**, 302 (1954).
²E. Callen and H. B. Callen, *Phys. Rev.* **139**, A455 (1965).
³B. R. Cooper, *Phys. Rev.* **169**, 281 (1968); in *Solid State Physics*, edited by F. Seitz and D. Turnbull (Academic, New York, 1968), Vol. 21, p. 393.
⁴D. A. Goodings and B. W. Southern, *Can. J. Phys.* **49**, 1137 (1971).
⁵E. A. Turov and V. G. Sharov, *Fiz. Tverd. Tela* **7**, 217 (1965) [*Sov. Phys.-Solid State* **7**, 166 (1965)].
⁶W. E. Evenson and S. H. Liu, *Phys. Rev.* **178**, 783 (1969).
⁷M. Rosen and H. Klimker, *Phys. Rev. B* **1**, 3748 (1970).
⁸B. R. Cooper, *Phys. Rev. Lett.* **19**, 900 (1967).
⁹J. J. Rhyne and S. Legvold, *Phys. Rev.* **138**, A507 (1965).
¹⁰P. A. Lindgård, *J. Phys. (Paris)* **32**, C1-238 (1971).
¹¹F. Keffer, *Handbuch Der Physik*, edited by S. Flügge (Springer, Berlin, 1966), Vol. XVIII/2, p. 168.
¹²J. Jensen, *Int. J. Magn.* **1**, 271 (1971).
¹³J. Jensen, Risø report No. 252, 1971 (unpublished).
¹⁴H. Chow and F. Keffer, *Phys. Rev. B* **7**, 2028 (1973).
¹⁵S. H. Liu, *Int. J. Magn.* **3**, 327 (1972).
¹⁶D. T. Vigen and S. H. Liu, *Phys. Rev. Lett.* **27**, 674 (1971); L. W. Hart and J. L. Stanford, *ibid.* **27**, 676 (1971).
¹⁷D. T. Vigen and S. H. Liu, *Phys. Rev. B* **5**, 2719 (1972).
¹⁸M. Nielsen, H. Bjerrum Møller, P. A. Lindgård, and A. R. Mackintosh, *Phys. Rev. Lett.* **25**, 1451 (1970).
¹⁹R. J. Elliott, A. P. Young, and S. R. P. Smith, *J. Phys. C* **4**, L317 (1971); J. R. Sandercock, S. B. Palmer, R. J. Elliott, W. Hayes, S. R. P. Smith, and A. P. Young, *J. Phys. C* **5**, 3126 (1972).
²⁰J. K. Kjems, G. Shirane, R. J. Birgeneau, and L. G. Van Uitert, *Phys. Rev. Lett.* **31**, 1300 (1973).
²¹S. B. Palmer (private communication).
²²J. J. Rhyne, *Magnetic Properties of Rare Earth Metals*, edited by R. J. Elliott (Plenum, London, 1972), Chap. 4.
²³P. A. Lindgård and O. Danielsen, *Phys. Rev. B* **11**, 351 (1975); O. Danielsen, Risø report No. 295, 1973 (unpublished).
²⁴T. Egami, *J. Phys. C* **5**, L85 (1972); M. S. S. Brooks and T. Egami, *J. Phys. C* **6**, 513 (1973).
²⁵D. E. Hegland, S. Legvold, and F. H. Spedding, *Phys. Rev.* **131**, 158 (1963).
²⁶B. F. DeSavage and A. E. Clark, in *Proceedings of the Fifth Rare Earth Research Conference*, Ames, Iowa, 1965 (unpublished).
²⁷P. De V. Du Plessis, *Philos. Mag.* **18**, 145 (1968).
²⁸S. B. Palmer, E. W. Lee, and M. N. Islam, *Proc. R. Soc. A* **338**, 341 (1974).
²⁹H. Bartholin, J. Beille, D. Bloch, P. Boutron, and J. L. Feron, *J. Appl. Phys.* **42**, 1679 (1971).
³⁰J. J. Rhyne and A. E. Clark, *J. Appl. Phys.* **38**, 1379 (1967).
³¹J. L. Feron, G. Huy, and R. Pauthenet, CRNS report No. 180, Paris, 1970, p. 19 (unpublished).
³²H. Bjerrum Møller, J. C. G. Houmann, J. Jensen, P. A. Lindgård, M. Nielsen, and A. R. Mackintosh, Risø report No. 256, 1972, p. 223 (unpublished).
³³J. Høg and P. Touborg, *Phys. Rev. B* **11**, 520 (1975).
³⁴S. Chikazumi, K. Tajima, and K. Toyama, *J. Phys. (Paris)* **32**, C1-179 (1971).
³⁵T. Asada, *J. Phys. Soc. Jpn.* **35**, 85 (1973).
³⁶P. Boutron, *Phys. Rev. B* **9**, 2971 (1974).
³⁷R. M. Nicklow and N. Wakabayashi, *Neutron Inelastic Scattering* (IAEA, Vienna, 1972), p. 611.
³⁸A. R. Mackintosh and H. Bjerrum Møller, *Magnetic Properties of Rare Earth Metals*, edited by R. J. Elliott (Plenum, London, 1972), Chap. 5.